



EUROfusion

EUROFUSION WPJET2-PR(16) 14788

E Pajuste et al.

**Tritium depth profile and desorption
from plasma facing beryllium materials
of ITER-Like-Wall at JET**

Preprint of Paper to be submitted for publication in
22nd International Conference on Plasma Surface Interactions
in Controlled Fusion Devices (22nd PSI)



This work has been carried out within the framework of the EUROfusion Consortium and has received funding from the Euratom research and training programme 2014-2018 under grant agreement No 633053. The views and opinions expressed herein do not necessarily reflect those of the European Commission.

This document is intended for publication in the open literature. It is made available on the clear understanding that it may not be further circulated and extracts or references may not be published prior to publication of the original when applicable, or without the consent of the Publications Officer, EUROfusion Programme Management Unit, Culham Science Centre, Abingdon, Oxon, OX14 3DB, UK or e-mail Publications.Officer@euro-fusion.org

Enquiries about Copyright and reproduction should be addressed to the Publications Officer, EUROfusion Programme Management Unit, Culham Science Centre, Abingdon, Oxon, OX14 3DB, UK or e-mail Publications.Officer@euro-fusion.org

The contents of this preprint and all other EUROfusion Preprints, Reports and Conference Papers are available to view online free at <http://www.euro-fusionscipub.org>. This site has full search facilities and e-mail alert options. In the JET specific papers the diagrams contained within the PDFs on this site are hyperlinked

Tritium depth profile and desorption from plasma facing beryllium materials of ITER-Like-Wall at JET

E.Pajuste¹, G.Kizane¹, A.Vitins^{1,2}, I. Igaune^{1,3}, L. Avotina^{1,3}, R. Zarins^{1,3}, JET contributors^{4*}

¹*Institute of Chemical Physics, University of Latvia, 1 Jelgavas St., Rīga, LV 1004, Latvia*

²*Institute of Solid State Physics, University of Latvia, 8 Kengaraga st., Riga, LV-1063, Latvia*

³*Faculty of Chemistry, University of Latvia, 1 Jelgavas St., Rīga, LV 1004, Latvia*

⁴*EUROfusion Consortium, JET, Culham Science Centre, Abingdon, OX14 3DB, UK*

elina.pajuste@lu.lv

Abstract

Tritium depth profile and its temperature programmed desorption rate were determined for selected samples cut out of beryllium tiles removed from the Joint European Torus vacuum vessel during the 2012 shut down. A beryllium dissolution method under controlled conditions was used to determine the tritium depth profile in the samples, whereas temperature programmed desorption experiments were performed to assess tritium release pattern. Released tritium was measured using a proportional gas flow detector. Prior to desorption and dissolution experiments, the plasma-facing surfaces of the samples were studied by scanning electron microscopy and energy dispersive X-ray spectroscopy.

Experimental results revealed that >95% of the tritium was localized in the top 30 - 45 μm of the plasma facing surface, however, possible tritium presence up to 100 μm cannot be excluded. During temperature programmed desorption at 4.8 $^{\circ}\text{C}/\text{min}$ in the flow of purge gas $\text{He}+0.1\% \text{H}_2$ the tritium release started below 200 $^{\circ}\text{C}$, the most intense release occurred at 450-640 $^{\circ}\text{C}$ and the degree of detritiation of >91% can be obtained upon reaching 800 $^{\circ}\text{C}$. The total tritium activity in the samples was in range of 2 - 32 kilo Becquerel per square centimetre of the plasma-facing surface area.

Highlights

- In ILW limiter beryllium tiles more than 95% of tritium is accumulated in the first 30-45 μm from the plasma facing surface, however, possible presence of tritium in low concentration up to the depth of 100 μm cannot be excluded.
- Highest tritium concentration can be found in the outer wall region of the vacuum vessel
- The degree of detritiation of samples from beryllium tiles >91% can be obtained upon reaching 800 $^{\circ}\text{C}$
- Erosion and melting of the beryllium can be observed in the central parts of the tiles, whereas side parts are mostly covered by the deposition layers.

Keywords

ITER-Like-Wall, beryllium, tritium, fuel accumulation, depth profile, thermal desorption

* See the Appendix of F. Romanelli et al., Proceedings of the 25th IAEA Fusion Energy Conference 2014, Saint Petersburg, Russia

1. Introduction

Currently the ITER-Like-Wall (ILW) project is being carried out at Joint European Torus (JET). This project aims to test materials relevant to ITER (International Thermonuclear Experimental Reactor). The first wall of the vacuum vessel is made of bulk beryllium and beryllium coated inconel tiles, whereas for the divertor bulk tungsten and tungsten coated carbon fibre composite tiles are used [1].

Performance of the wall materials is mostly limited by the surface erosion and tritium retention. Long term fuel retention is not only economical but also radiological issue due to radioactivity of tritium.

There have been number of separate experiments with deuterium-tritium mixtures in which tritium have been introduced in JET. Most recent tritium experiment was performed in 2003 - Trace Tritium Experiment –TTE [2]. Tritium has not been introduced within ILW campaign yet, however tritium has remained in the vacuum vessel since D-T experiments; moreover it can be produced in the D-D reactions and also in the beryllium reactions with neutrons themselves.

Tritium accumulation in wall materials can occur as a result of its co-deposition with eroded particles and implantation/diffusion in the bulk of the wall materials.

Aim of this study is to assess tritium accumulation in the beryllium wall materials and factors affecting it. Tritium content, its depth profile and thermal desorption pattern were studied, as well as structure and chemical composition of the plasma facing surface.

2. Experimental

2.1. Samples investigated

In this study, tiles exposed in JET during the first year of JET-ILW operation (2011-2012) were analysed. During this period total operational time was 19 h including dedicated discharges in limiter configuration to assess Be erosion [3]. During the shutdown that followed the first ILW campaign, a number of tiles were retrieved for *post-mortem* analysis. Tiles used in this study were from the upper region (Upper Dump Plate) and mid-region (inner wall - Inner Wall Guard Limiter (IWGL), and outer -Wide Poloidal Limiter (WPL)) of the vessel (Fig.1).

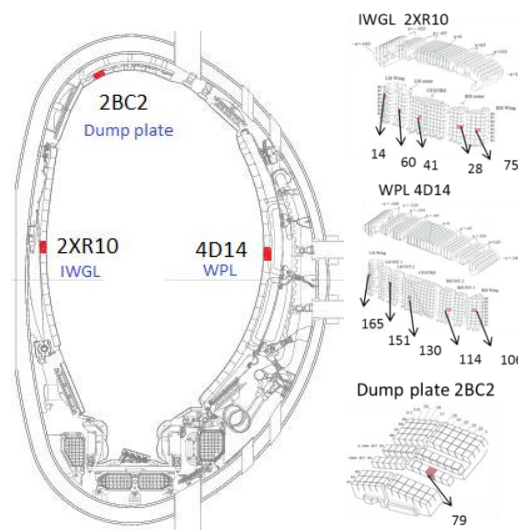


Fig. 1 Position of the analysed samples in vacuum vessel and tiles


Samples of approximately 1.2×1.2×1.0 cm cut out of tiles (as described in [4]) were used in the present study. These samples were further cut into two parts in order to perform tritium depth profiling and desorption experiments. During cutting of the samples, their temperature was controlled not to exceed ~60°C in order to avoid tritium loss as a result of thermal desorption.

2.2. Surface structure and chemical composition analysis

Methods of Scanning electron microscopy (SEM) and Energy dispersive X-ray Spectroscopy (EDX) were used for surface structure and chemical composition analysis. Scanning electron microscope *Hitachi S-4800* and EDX detector *Quantax Esprit 1.9* were used in this study.

2.3. Determination of tritium depth profile

Tritium (T) depth profile was measured by the dissolution method using the setup schematically shown in Fig. 2. In this method, successive layers of Be were removed using 1 mol/L sulphuric acid and amount of evolved hydrogen and released tritium were measured. Following processes are taking place during the dissolution:



In the 1 mol/L sulphuric acid molecular T_2 and atomic T^0 (interstitial) tritium of the activities A_{T_2} and A_{T^0} respectively, present in a Be sample transfer as T_2+HT into a flow of carrier gas, where the tritium activity was measured with tritium monitor TEM 2100A with a proportional gas flow-through detector DDH 32.

$$A_{T, gas\ ph.} = A_{T_2} + A_{T^0} \quad (6)$$

Chemically bonded tritium (depicted as T^+ in the processes schemes) localized in a Be layer remains in the solution and the tritium activity $A_{T, liquid\ ph.}$ was measured with liquid scintillation method. Solution containing tritium was distilled and 5 mL aliquot mixed with 15 mL of Ultima Gold scintillation cocktail and analysed for total tritium with a TRi-Carb 2910TR counter [PerkinElmer, Inc].

Amount of tritium atoms can be calculated by means of the tritium decay constant $\lambda = 1,78 \cdot 10^{-9} s^{-1}$ [5]

$$N_T = \frac{A_T}{\lambda} \quad (7)$$

Calculations on tritium distribution in the bulk of the sample are based on the controlled dissolution process. One hydrogen molecule corresponds to one beryllium (Eq 1 and 2) atom and the dissolution rate of beryllium and hereby also the thickness of dissolved layer L_t at the moment t can be calculated from the number hydrogen molecules evolved, $N_{H_2,t}$.

$$L_t = \frac{N_{H_2,t} \cdot M_{Be}}{N_A \cdot \rho_{Be} \cdot S_{Be, dis}} \quad (8)$$

where M_{Be} - beryllium atomic mass (9.012 u), N_A –Avogadro constant ($6.022 \cdot 10^{23} mol^{-1}$), ρ_{Be} - beryllium theoretical density (1.85 g/cm³) and $S_{Be, dis}$ (cm²) - surface area of the beryllium sample being etched by the acid.

Tritium concentration (atomic parts per million appm) in the sample is calculated as the ratio of released tritium atoms and dissolved beryllium in the time period Δt .

Resolution of this method is ~10µm. The resolution is determined by the sample properties (porosity, grain size), geometry of the setup (volumes of the dissolution cell, the column filled with silica gel and tritium detector), the flow rate of the argon carrier gas and the rate of dissolution of the beryllium sample in 1 mol/L sulphuric acid.

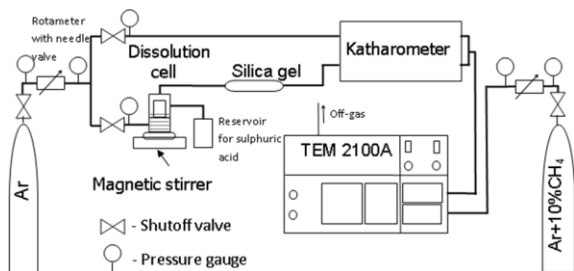


Fig. 2. Dissolution setup

2.4. Thermal desorption of tritium

Thermal desorption of tritium was performed in a flow of He + 0.1% H₂ purge gas at 14-15 L/h, using the setup schematically shown in Fig. 3. The quartz tube in the setup had two compartments – one for the sample in a porcelain boat and one for a bed of granulated zinc. The quartz cap had a thermocouple channel – an inner quartz tube sealed towards the sample. The zinc bed at 390-400 °C converts tritiated water to molecular gaseous tritium (HT, DT, and traces of T₂). In order to prevent the tritium detector from being contaminated with tritiated compounds of low volatility, the flow of He + 0.1% H₂ purge gas after the zinc bed was passed through a column with silica gel “Silcarbon SGB 50” and a cold trap immersed in a Dewar flask with dry ice in acetone at about -50 to -80 °C. Before entering a tritium monitor TEM 2102A, the flow of He + 0.1% H₂ purge gas was directed through a fritted glass filter. Samples were heated at a rate of 4.8 °C/min to 1030 °C and then kept at that temperature for 1 h. The temperatures of the sample, the zinc bed and the cold trap were continuously measured. The tritium activity in the purge gas was continuously monitored using a proportional counter with an operating volume of 300 cm³ and a tritium monitor TEM 2102A. The total released tritium activity was calculated by integrating the release rate over the time where a release was measurable. The radioactivity of tritium released was calculated as kBq/cm² to 1 cm² of the plasma-facing surface area of the sample. As the subsequent second heating of the same sample in the same setup with the same temperature program to 1030 °C caused no appreciable tritium release, the tritium release in the first heating was considered as a complete tritium release with no appreciable residual tritium amount remaining in the sample. As most of tritium released during the temperature ramp of 4.8 °C/min to 1030 °C, the release rate and the sum release were plotted as functions of temperature.

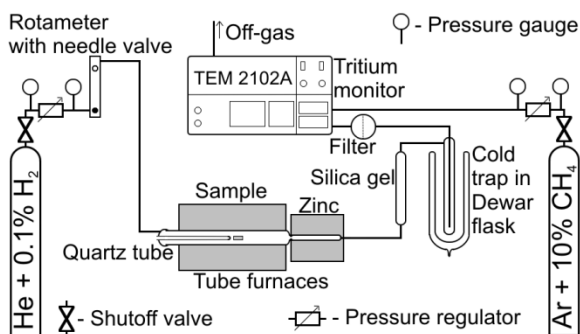


Fig. 3 Tritium desorption setup

Both dissolution and desorption methods give information on tritium content in the samples. However, dissolution method gives only information on tritium accumulated in beryllium, whereas by desorption method tritium from deposition layer is also measured.

3. Results

3.1. Surface structure and chemical composition

Analysis of the surface was performed to estimate effects of the conditions the samples have been exposed to - if there has been any melting, plasma etching or formation of deposition layer.

Inner Wall Guard limiter IWGL

Results of SEM and EDX analysis revealed that surface of central part of the tile (sample 41) is comparably clean (almost no deposition). Prolonged beryllium structures can be observed (Fig.4) that might indicate the plasma induced erosion. Similar surface morphology has been reported after light ion plasma exposure of beryllium in plasma device Pisces-B [6].

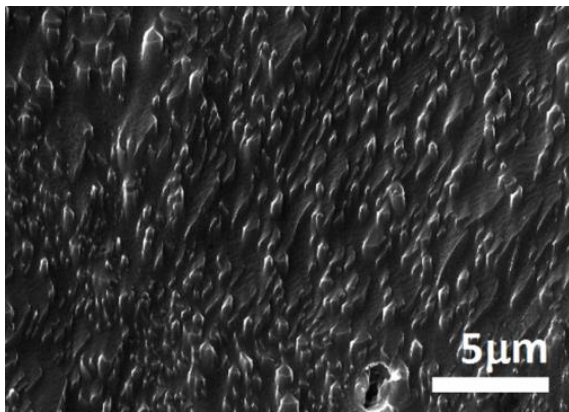


Fig. 4 SEM micrographs of sample No 41 showing prolonged beryllium structures

Outer part of the tile (samples 60, 28) have surface coated with a deposition layer of “scale like” structure (Fig.5). According to EDX data deposition layer contains nickel, oxygen, carbon and traces of tungsten and iron.

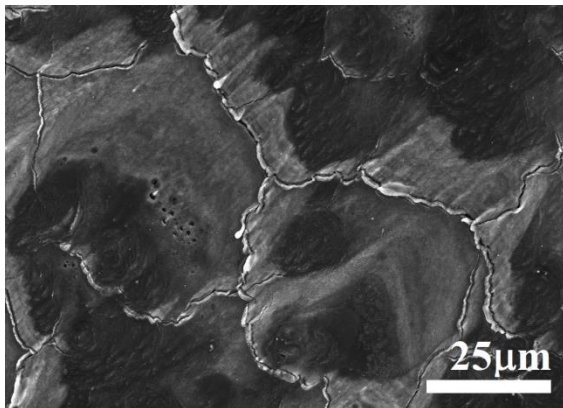


Fig. 5 SEM micrograph of sample No 60 showing scale like deposition layer

Wing part of the tile (samples 14 and 75) has “cabbage like” deposition layer with melted/resolidified beryllium droplets on the surface of it. Irregular and prolonged shape droplets of melted and then solidified beryllium can be found randomly on the surface of the deposition layer (Fig. 6). These droplets of the beryllium have a micro/nano scaled porosity. The structure of the melted beryllium corresponds well to the results on exposing Be to the plasma loads outside the vessel [7].

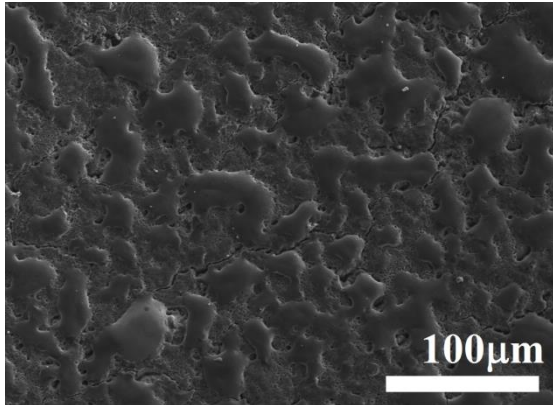


Fig. 6 SEM micrograph of sample No 75 showing melted/resolidified beryllium droplets

In the erosion studies at JET strong melting has been described in the mid-plane region on inner limiter and this part is a net erosion zone as a result of interaction with limiter plasmas. It corresponds well to the structure of the central part of the tile. Moreover, this molten material has travelled in an upward poloidal direction due to $j \times B$ Lorentz forces and plasma pressure [8]. It might explain the prolonged shape of the molten beryllium droplets.

Wide Poloidal Limiter WPL

Results of the SEM and EDX analysis revealed that surface of the central part of the tile from WPL (sample 130) has similar prolonged beryllium structures as were observed on the central part of the tile from IWGL 2XR10 (sample no. 41). However, above these structures a deposition layer is present. It might indicate that plasma induced erosion of beryllium was less intense and was followed by lower temperature regime when deposition layer was formed.

Outer part of the tile has a deposition layer with microparticles of high nickel concentration on the surface of it. Moreover these particles are deposited on the surface in a specific pattern - as parallel lines that are visible also by a naked eye (Fig.7).

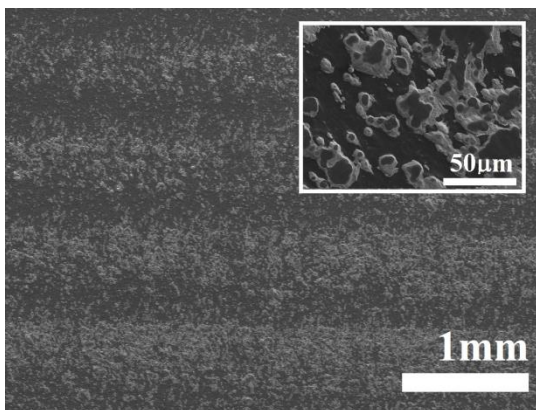


Fig. 7 SEM micrograph of sample No 114 showing microparticles of high nickel content organized as parallel lines

Samples from the left and right wings of the tile (no. 106 and 165) are covered with the layer of melted/resolidified beryllium (Fig. 8). This layer has cracks and bubbles from which part has “exploded”. Moreover, in areas of the bubbles, increased oxygen content was observed. Resolidified beryllium layer is partly delaminated from the sample no. 106 and reveals a layer of high nickel content below it.

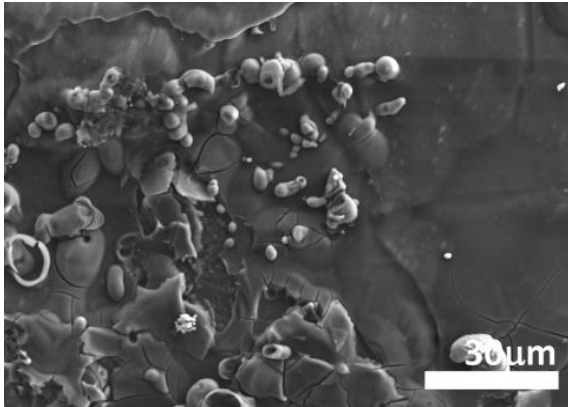


Fig. 8 SEM micrograph of sample No 165 showing bubbles of melted/resolidified beryllium

Upper Dump Plate

Surface structure of the sample from outer part of the Upper Dump Plate tile is similar to the structure of inner wall tile outer part. Surface is covered by the “cabbage like” deposition layer with melted beryllium droplets on it.

3.2. Tritium content and depth profile

Tritium content in the samples was measured both by the dissolution method and thermal desorption (Fig.9). More precise values give thermal desorption results since they include also tritium accumulated in the deposition layer. For instance, WPL sample 165 had the tritium content of 19.7 kBq/cm² as determined by the dissolution method and 32.3 kBq/cm² as determined by the thermal desorption. Results revealed that higher tritium concentrations can be found in the samples from the outer wall (WPL). In the WPL samples tritium content was from 7.5 kBq/cm² (4.2×10^{12} atoms/cm²) in sample 114 to 32.3 kBq/cm² (18.1×10^{12} atoms/cm²) in 165, whereas in the IWGL samples highest concentration was found to be 7.5 kBq/cm² (4.2×10^{12} atoms/cm²) in sample 60. In the sample from Upper Dump Plate tritium concentration was 4.5 kBq/cm² (2.5×10^{12} atoms/cm²)

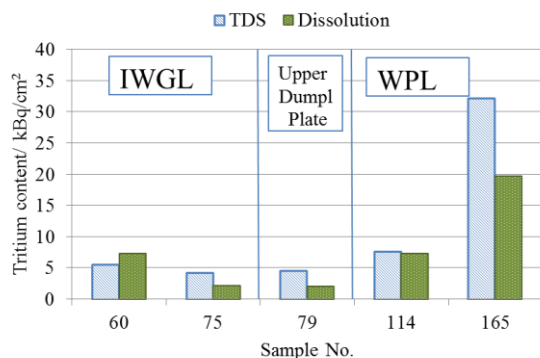


Fig. 9 Tritium content in beryllium samples from IWGL (60, 75), Upper Dump Plate (79) and WPL (114, 165)

Tritium depth profile measurement shows that 95% of tritium is accumulated in the first 30 – 45 μm from the plasma facing surface. In the sample of high tritium content – 165 from the WPL, low concentration of tritium can be found up to 100 μm.

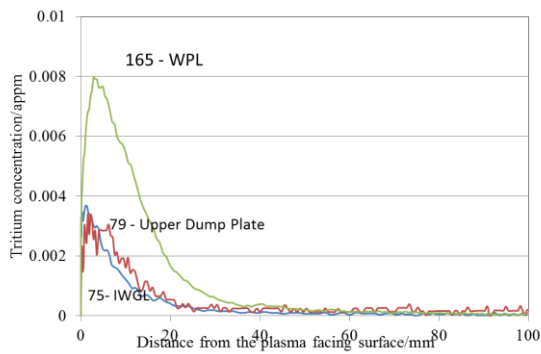


Fig.10 Tritium depth profile of beryllium samples 75 from IWGL (blue), 165 from WPL (green) and 79 from Upper Dump Plate (red)

3.3. Tritium thermal desorption

According to the results of tritium thermal desorption experiments, samples 60 and 75 (IWGL), 79 (Upper Dump Plate), 114 and 165 (WPL) had the following values of their total tritium content, which were defined as their final values of the tritium sum release for 1 cm² of the plasma-facing surface area: 5.5, 4.2, 4.5, 7.6 and 32.3 kBq/cm², respectively. Though the values of the total tritium content of the samples are quite different, their tritium release patterns can be clearly compared by calculating and plotting their tritium release rate and sum release as fractions with respect to their final values of the tritium sum release. Curves thus obtained for the tritium release rate and sum release are shown in Figs. 11a and 11b respectively.

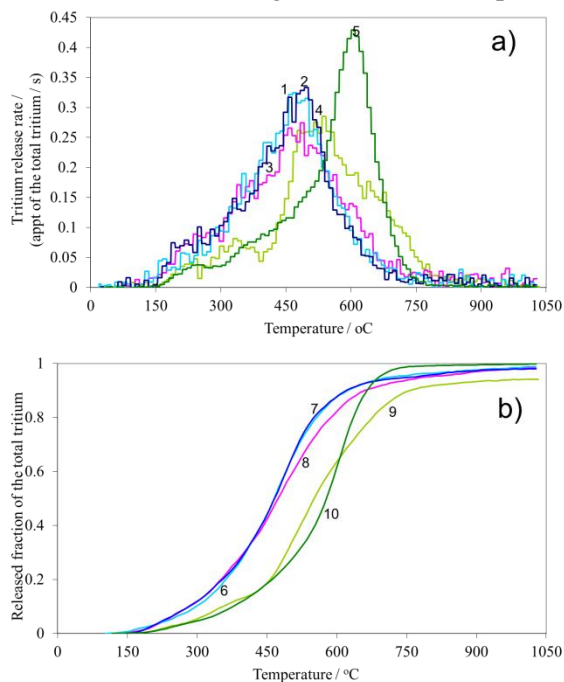


Fig. 11. Spectra of temperature-programmed desorption of tritium at the rate of temperature increase of 4.8 °C/min for the samples having respective final values of the tritium sum release for 1 cm² of the plasma-facing surface area: curves 1 and 6 (sky blue) – sample 75 of IWGL, 4.2 kBq/cm²; curves 2 and 7 (dark blue) – sample 60 of IWGL, 5.5 kBq/cm²; curves 3 and 8 (pink) – sample 79 of the Upper Dump Plate, 4.5 kBq/cm²; curves 4 and 9 (lime) – sample 114 of WPL, 7.6 kBq/cm²; curves 5 and 10 (green) – sample 165 of WPL, 32.3 kBq/cm².

Samples 60 and 75 of IWGL and sample 79 of the Upper Dump Plate had their total tritium content in the range 4.2-5.5 kBq/cm², but their fractional release rate and released fraction as functions of temperature were quite similar (curves 1-3 of Fig. 11a and curves 6-8 of Fig. 11b). Their curves of the fractional release rate had a single distinct maximum: the tritium release started at 100-150 °C, reached its maximum rate at 450-500 °C, and, upon reaching 750 °C, more than 93% of the total tritium were released. Sample 79 of the Upper Dump Plate had a slightly broader maximum and more gradual descent of the fractional tritium release rate than samples 60 and 75 of IWGL (curve 3 vs. curves 1 and 2 of Fig. 11a, curve 8 vs. curves 6 and 7 of Fig. 11b).

It is evident from Fig. 11 that samples 114 and 165 of WPL had tritium release patterns that differ from those of samples 60 and 75 of IWGL and that of sample 79 of the Upper Dump Plate. Though the tritium release started also at 100-150 °C, the fractional tritium release rate of samples 114 and 165 of WPL had a distinct shoulder at 150-400 °C (sample 114) or at 150-500 °C (sample 165) that preceded the main maximum at 460-560 °C (sample 114) or at 560-640 °C (sample 165). Sample 114 had a more gradual descent of the fractional tritium release rate than sample 165 in the temperature range of 700-850 °C. Upon reaching 800 °C, the degree of detritiation of all the samples investigated was more than 91%.

4. Discussion

Results of structural analysis show that there has been plasma induced erosion from the central part of the IWGL and WPL tiles and melted material has transferred to the sides of the tiles where it has resolidified. Comparison of the tritium concentration in different positions on the tile reveals that there is less tritium in plasma wetted regions and its highest concentration can be found in the regions where melted material is present. For example, sample from the central part of the WPL tile that has evidences of direct plasma impact contains 7.5kBq/cm² of tritium, whereas it's outer part with deposition layer and resolidified beryllium – 32.3 kBq/cm². Tritium accumulation depends also on the tile position in the vacuum chamber – it is more intense in the outer wall tiles than that in the upper region or inner wall. These results correspond well to the measured deuterium concentration by other authors [9]. Moreover, tritium desorption experiments showed that maximum release rate for samples from the outer wall is reached at higher temperatures. However, degree of 90% detritiation is reached at 765oC for all the samples investigated in the present study.

Conclusions

- Tritium content is higher in the outer wall Be limiter tiles (7.5-32.3kBq/cm²) than that in inner wall and upper region tiles (4.1 -7.5kBq/cm²).
- Plasma - wetted regions contain less tritium, highest tritium concentrations can be found in areas where melted beryllium from these regions has been transferred.
- Tritium desorption from beryllium samples started at 100-150 °C, had a maximum rate at 450-640 °C, and at 800 °C the degree of detritiation was more than 91%.
- Tritium desorption patterns of samples from the outer wall Be limiter tiles are significantly different from those of samples from the inner wall and upper region tiles.
- 95% of tritium is accumulated in the first 30 - 45 µm, however, possible presence of tritium in low concentration up to the depth of 100 µm cannot be excluded.

References

- [1] G.F. Matthews, M. Beurskens, S. Brezinsek, M. Groth, E. Joffrin, A. Loving, M. Kear, M.L. Mayoral, R. Neu, P. Prior, V. Riccardo, F. Rimini, M. Rubel, G. Sips, E. Villedieu, P.d. Vries, M.L.

Watkins, EFDA JET contributors, JET ITER-like wall—overview and experimental programme, *Physica Scripta* T145 (2011) 014001.

[2] T.T.C. Jones, EFDA JET Contributors, Technical and Scientific Aspects of the JET Trace-Tritium Experimental Campaign, *Fusion Science and Technology* 48 (2005) 250-257.

[3] S. Brezinsek, Plasma-surface interaction in the Be/W environment: Conclusions drawn from the JET-ILW for ITER, *Journal of Nuclear Materials* 463 (2015) 11-21.

[4] A. Widdowson, A. Baron-Wiechec, P. Batistoni, E. Belonohy, J.P. Coad, P. Dinca, D. Flammini, F. Fox, K. Heinola, I. Jecu, J. Likonen, S. Lilley, C.P. Lungu, G.F. Matthews, J. Naish, O. Pompilian, C. Porosnicu, M. Rubel, R. Villari, JET Contributors, Experience of handling beryllium, tritium and activated components from JET ITER like wall, *Physica Scripta* 2016 (2016) 014057.

[5] Lucas, L.L.; Unterweger, M.P. Comprehensive review and critical evaluation of the half-life of tritium, *Journal of Research of the National Institute of Standards and Technology*, 105, 4 (2000). 541-549

[6] R.P. Doerner, M.J. Baldwin, D. Nishijima, Plasma-induced morphology of beryllium targets exposed in PISCES-B, *Journal of Nuclear Materials* 455 (2014) 1-4.

[7] I.B. Kupriyanov, G.N. Nikolaev, L.A. Kurbatova, N.P. Porezanov, V.L. Podkovyrov, A.D. Muzichenko, A.M. Zhitlukhin, A.A. Gervash, V.M. Safronov, Erosion of beryllium under ITER – Relevant transient plasma loads, *Journal of Nuclear Materials* 463 (2015) 781-786.

[8] A. Widdowson, E. Alves, C.F. Ayres, A. Baron-Wiechec, S. Brezinsek, N. Catarino, J.P. Coad, K. Heinola, J. Likonen, G.F. Matthews, M. Mayer, M. Rubel, JET Contributors, Material migration patterns and overview of first surface analysis of the JET ITER-like wall, *Physica Scripta* 2014 (2014) 014010.

[9] K. Heinola, A. Widdowson, J. Likonen, E. Alves, A. Baron-Wiechec, N. Barradas, S. Brezinsek, N. Catarino, P. Coad, S. Koivuranta, S. Krat, G.F. Matthews, M. Mayer, P. Petersson, JET Contributors, Long-term fuel retention in JET ITER-like wall, *Physica Scripta* 2016 (2016) 014075.

Acknowledgements

This work has been carried out within the framework of the EUROfusion Consortium and has received funding from the Euratom research and training programme 2014-2018 under grant agreement No 633053. The views and opinions expressed herein do not necessarily reflect those of the European Commission