



EUROfusion

WPMAT-CPR(17) 17544

JW Coenen et al.

Tungsten fiber-reinforced tungsten (Wf/W)

Preprint of Paper to be submitted for publication in Proceeding of
18th International Conference on Fusion Reactor Materials
(ICFRM-18)



This work has been carried out within the framework of the EUROfusion Consortium and has received funding from the Euratom research and training programme 2014-2018 under grant agreement No 633053. The views and opinions expressed herein do not necessarily reflect those of the European Commission.

This document is intended for publication in the open literature. It is made available on the clear understanding that it may not be further circulated and extracts or references may not be published prior to publication of the original when applicable, or without the consent of the Publications Officer, EUROfusion Programme Management Unit, Culham Science Centre, Abingdon, Oxon, OX14 3DB, UK or e-mail Publications.Officer@euro-fusion.org

Enquiries about Copyright and reproduction should be addressed to the Publications Officer, EUROfusion Programme Management Unit, Culham Science Centre, Abingdon, Oxon, OX14 3DB, UK or e-mail Publications.Officer@euro-fusion.org

The contents of this preprint and all other EUROfusion Preprints, Reports and Conference Papers are available to view online free at <http://www.euro-fusionscipub.org>. This site has full search facilities and e-mail alert options. In the JET specific papers the diagrams contained within the PDFs on this site are hyperlinked

Improved Pseudo-Ductile Behavior of Powder Metallurgical Tungsten short fiber-reinforced tungsten (W_f/W)

J.W. Coenen^a, Y.Mao^a, S.Sistla^b, J.Riesch^c, T.Hoeschen^c, and Ch.Broeckmann^b, R.Neu^{c,d}, Ch.Linsmeier^a

^aForschungszentrum Jülich GmbH, Institut fuer Energie und Klimaforschung 52425 Juelich, Germany

^bLehrstuhl für Werkstoffanwendungen im Maschinenbau, RWTH Aachen, 52062 Aachen Germany

^cMax-Planck-Institut für Plasmaphysik, 85748 Garching, Germany

^dTechnische Universität München, Boltzmannstrasse 15, 85748 Garching, Germany

Abstract

For the first wall of a fusion reactor unique challenges on materials in extreme environments require advanced features in areas ranging from mechanical strength to thermal properties. The main challenges include wall lifetime, erosion, fuel management and overall safety. For the lifetime of the wall material, considerations of thermal fatigue due to transient heat loading are crucial as severe mechanical and thermal loads during operation are expected.

Tungsten (W) is the main candidate material for the first wall of a fusion reactor as it is resilient against erosion, has the highest melting point of any metal and shows rather benign transmutation behavior under neutron irradiation. However, Tungsten has an issue related to intrinsic brittleness as well as operational embrittlement. To overcome this, a W-fiber enhanced W-composite material (W_f/W) incorporating extrinsic toughening mechanisms has been developed. Recently progress has been made in the Powder Metallurgical routes towards fully dense multi short-fiber W_f/W . For reasonable performance with respect to mechanical properties and hydrogen retention a fully dense pseudo-ductile W_f/W with is crucial. The properties of the used fibres are crucial they should retain some level of ductility.

In this contribution it is shown that excluding or minimising the impact of carbon impurities during the sintering process can significantly improve the mechanical properties of the fibres. New test results on the behaviour of PM W_f/W with and without a diffusion barrier during the sintering show a clear benefit as the fibres can retain ductility. Not the grain growth during sintering but the carbon present during sintering is clearly identified as determining the mechanical properties of the fibres.

Keywords:

1. Introduction

Tungsten (W) is currently the main candidate material for the first wall and in particular for highly loaded components of the divertor of a future fusion reactor as it is resilient against erosion, has the highest melting point, shows rather benign behavior under neutron irradiation, and low tritium retention. Extensive work has been done to qualify current materials with respect to these issues for ITER [1, 2, 3]. For the next step devices, e.g. DEMO, or a future fusion power plant the limits on power exhaust, availability, lifetime and not least on fuel management are quite more stringent. Extensive studies and materials programs [4, 5, 6] have already been performed hence it is assumed that the boundary conditions [7] to be fulfilled for the materials are in many cases above the technical feasibility limits as they are set today [1, 2]. Efforts to establish new advanced plasma-facing material-options are moving forward [2, 8] focussing on crack resilient materials with low activation, minimal tritium uptake, long lifetime and low erosion. Many advanced materials base their improved properties on the use of a composite approach. One Concept is based on the incorporation of fibres, energy dissipating mechanisms, like ductile deformation of fibres, fibre pull-out, and crack bridging and de-

flexion are facilitated [9, 10, 11]. An issue not tackled in this contribution is the formation of radioactive and highly volatile W-oxide (WO_3) compounds during accidental air ingress. To suppress the release of W-oxides W-based self-passivating alloys can be incorporated into the composite approach [12, 13, 14]. In this contribution the focus lies on the improvement of the powder-metallurgical (PM) production W_f/W as plasma-facing-material (PFM). The influence of the die material used is has been explored. It was shown that the ductile deformation [15] as well as the high strength [16] of the tungsten wire have a significant influence on the overall properties of W_f/W . Mueller et al [17] show that one of the crucial aspects of the production process of any tungsten fibre composite is to control the amount of impurities e.g. carbon during the consolidation process. Carbon is of particular interest with respect to W and its mechanical properties [18].

2. Tungsten-Fibre Reinforced Tungsten

To overcome the brittleness issues when using W, a W fibre enhanced W composite material (W_f/W), incorporating extrinsic toughening mechanisms can be used. The short fibres used in this PM version of W_f/W are shown in Fig. 1. Yttria is used

as the interface material in order to allow the energy dissipation mechanisms to become active. Yttria is an ideal candidate as the interface material for the W_f/W composite due to its several advanced properties: good thermal and chemical stability, high mechanical strength and hardness. [8, 19]. Various meth-

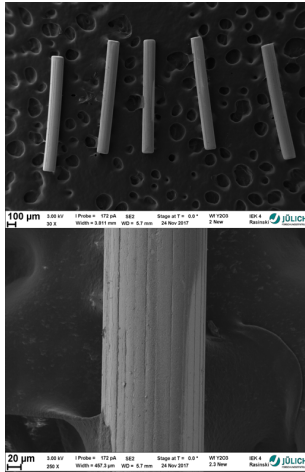


Figure 1: Short W-fibres coated by 2.5μ Yttria interface

ods of building and constructing W_f/W composites, either via Chemical Vapor Deposition (CVD) [20, 21] or powder metallurgical processes [22, 23] are available. Based on the work presented here and previous work [15, 24, 22, 16, 25], the basic proof of principle for CVD & PM W_f/W has been achieved. One of the crucial issue is to maintain as much of the properties of the constituents even after exposing the material to the production cycle and the fusion environment. This allows for better extrinsic toughening and pseudo-ductile behaviour.

It can be expected that when using doped W-wires they will e.g. retain their ductility even at elevated temperatures (above 1500 K) [15] and all mechanisms necessary for pseudo-ductility will be enabled [24, 8, 25]. Properties of the fibres might be degraded by various circumstances e.g. by impurities during fabrication, high-temperatures [17] or neutron irradiation during operation [26, 27]. Even if the fibres lose their ductility however, the pull-out of fibres and the crack deflection needs still to deliver some pseudo-ductility for a viable material option.

In the following we will describe that one aspect of the production needs to be controlled with particular care to minimise the degradation of the material properties of the fibres.

2.1. W_f/W - Material Production

For powder-metallurgical production of W_f/W as already described in [25, 8] the homogenous introduction of powder between the fibres is required for good material properties, hence short fibres are used in contrast to e.g. woven preforms or parallel long fibres as used in the CVD process route. Based on Results from [8] pressure-less sintering of W_f/W was unsuccessful, additional external pressure during sintering of W_f/W is required to get a dense and crack-free sample. Field Assisted Sintering Technology (FAST) [28] provides such additional compaction during sintering. Details on the consolidation

incl. HIP (Hot-isostatic-Pressing) as well as material properties can be found in [8, 25].

Potassium doped W-fibres with $150 \mu\text{m}$ diameter and 2.4 mm length (OSRAM), together with pure W-powders (OSRAM) (average particle size $5 \mu\text{m}$) were used as raw materials. The FAST process gives rise to pressure and high temperatures temperature on the interface and can thus cause a thin interfaces to dissipate [29, 30, 31]. Here $2.5 \mu\text{m}$ thick yttria is applied for a viable interface similar to the work given in [25]. The fibres and powders were mixed homogeneously before sintering, in order to produce a W_f/W sample with a random fibre distribution and orientation. A density of $\sim 94\%$ was achieved after applying the sintering process at 2173 K (4 min) and 60 MPa (heating rate 200 K/min) [25, 8]. In all cases a fibre-volume-fraction of 30% was used.

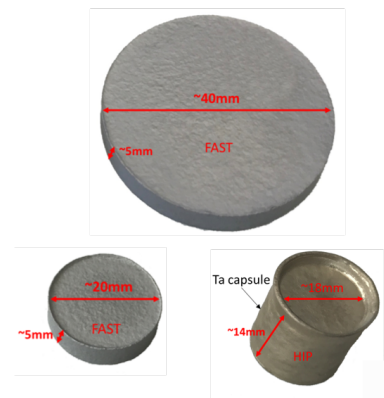


Figure 2: Large 40mm FAST W_f/W Sample displayed next to a small 20mm FAST and HIP samples. [25]

Samples have been prepared to establish if and how pseudo-ductility can be achieved in the case of a randomly distributed short fibre W_f/W and also which role the interface and impurity content may play. Here the main parameter that was changed in comparison to [25, 8] is the addition of a tungsten foil to prevent as much as possible the interaction of the die material with the samples that are being sintered.

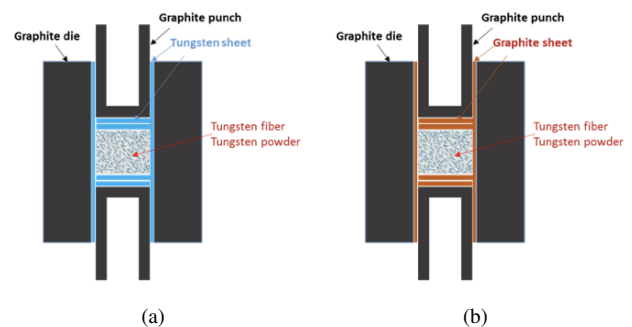


Figure 3: Two different procedures for consolidation have been used to test the influence of the die material onto the final material properties (a) Tungsten foil as diffusion barrier, (b) graphite sheets for lubrication

In figure 3 a sketch of the two different FAST procedures used is given. In one case the powder and die are separated by a graphite foil while in the other case a thin tungsten foil is used.

Based on FAST samples with 20 and 40 mm diameter and a height of 5 mm were produced as shown in Fig. 2.

2.2. W_f/W - Material Structure

Figure 4, shows a representative cut through PM- W_f/W after consolidation as described above. The materials is dense and a thin interface of yttria remains around the randomly distributed fibres. The microstructure is identical for both consolidation procedures.

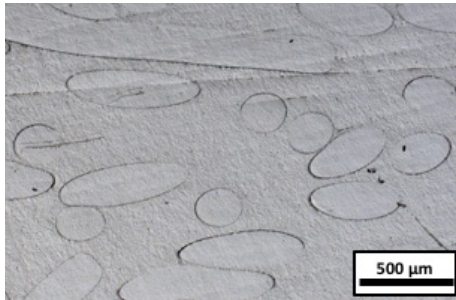


Figure 4: Overview Microstructure after sintering, with-out tungsten foil

For both consolidation procedures shown also the microstructure of the fibre was studied. Figure 5 shows for both cases similar grain size and structure after FAST. Originally the fi-

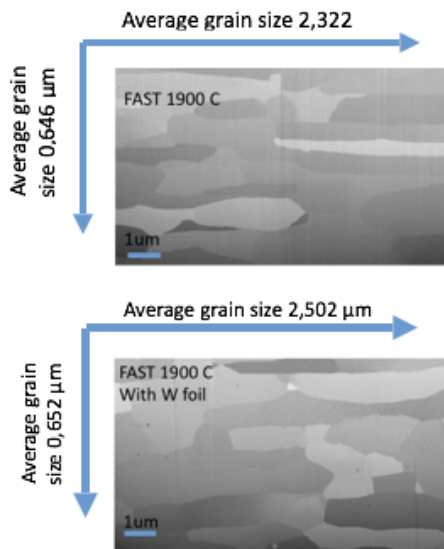


Figure 5: Grainstructure and grain size of the fibres after sintering

bres have a very fine filamented grain structure as given in [32] with (0.3-1.5) μm in the directions perpendicular to the wire axis and roughly 10-90 μ along the axis. After consolidation of the W_f/W samples the average grain size along the original drawing direction of the fibre the is determined to be 2.322, and 2.502 μm respectively while perpendicular to the drawing direction the grains have an extent of around 6.5 μm . The grain size measurement is based on the Lineal Intercept Procedure (ASTM E 112) using SEM images. The average grain size is determined by the number of times a test line cuts across, or is tangent to, grain boundaries.

It is clear that the sintering can have consequences for the grain structure as seen in the micrographs. The main message here is however that for both cases, with and without W-foil a similar microstructure modification has taken place without a significant difference between the two procedures.

3. W_f/W - Pseudo-ductility

To investigate the impact of the change in production procedure onto the toughening, fracture mechanical tests were performed on notched samples. Small bar shaped (18 \times 2 \times 4 mm) three point bending test samples were produced and a pre-notch introduced by means of diamond wire saw and manual razor blade polishing. Utilizing an Instron 3342 universal testing machine (Instron GmbH) three point bending tests were performed and load displacement curves were taken. Fracture surfaces were analysed to establish if the desired mechanisms can be observed. A series of tests have been performed and published in [8, 25], all based on the FAST method using a graphite sheet. A typical curve is given in Fig. 6. The curves are given in arbitrary units to show the behaviour of a W_f/W sample. As the notches are not produced reproducibly the absolute values can not be compared. c Even after crack initiation is observed

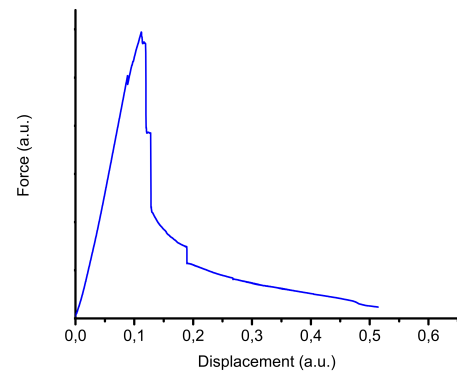


Figure 6: 3pt bending test results of W_f/W produce via FAST with C-Foil

an increased load can still be handled. This is a clear indication of pseudo-ductility in this simple model-system.

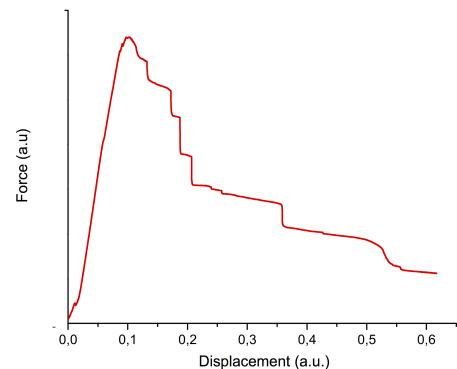


Figure 7: 3pt bending test results of W_f/W produce via FAST with W-Foil

In Fig. 7 a similar curve is given taken with material utilising a tungsten foil during consolidation. One major difference is the shape of the curve. The fall off in load is far smoother and more steps are visible indicating a different fracture behaviour of both samples.

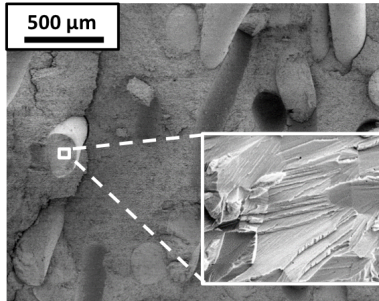


Figure 8: Fracture Surfaces of a W_f/W samples consolidated with C-foil

In figure 8 and 9 thus the typical fracture surfaces are depicted to elaborate on the difference in production. Figure 8 shows the clear brittle fracture of one of the constituent short fibres with a clear intra-granular cleavage fracture.

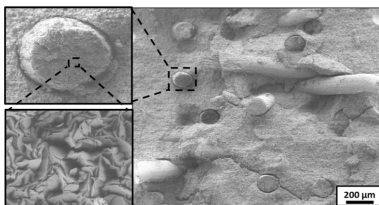


Figure 9: Fracture Surfaces of a W_f/W samples consolidated with W-foil

For the Fig. 9 a ductile behaviour of the fibre is observed allowing for more energy dissipation also indicative from the stress strain curve. The fracture shows fibre necking with knife edges and a sharp fracture surface. This behaviour is in line with the results by Mueller et al. [17]. It was found that carbon when present during the annealing process of fibres can embrittle them already when diffusing in small quantities into the fibre. This is in line with findings from literature[18] where a link was established between the interstitial impurities such as carbon and the low temperature tensile properties of tungsten. In the given work above all presented test have been performed at room temperature to represent the worst case scenario for tungsten. Especially here pseudo-ductility is required. Minimisation of the impact of the production process by excluding carbon is one step towards optimisation.

4. Conclusion and Outlook

Based on the presented tests for PM- W_f/W with W-foil it can be said that the manufacturing path for W_f/W has been further improved. The presented approach utilising a W-Foil mitigates the embrittlement of the constituent fibres during FAST processing.

Based on these results it can be seen that improved pseudo-ductile behaviour can be achieved for PM- W_f/W . It is planned

to utilise this new route in developing prototype components for application in existing fusion devices. In order to also establish material performance under irradiation PM - W_f/W samples (cf. figure 2) are earmarked for irradiation in a nuclear reactor starting in 2018.

Acknowledgement

The authors want to acknowledge support by Osram GmbH, Schwabmünchen, Germany for providing the powder and fruitful discussions about the new material. This work has been carried out within the framework of the EUROfusion Consortium and has received funding from the Euratom research and training programme 2014-2018 under grant agreement No 633053. The views and opinions expressed herein do not necessarily reflect those of the European Commission.

- [1] V. Philipps. Tungsten as material for plasma-facing components in fusion devices. *Journal of Nuclear Materials*, 415(1):2–9, 2011.
- [2] JW Coenen, S Antusch, M Aumann, W Biel, J Du, J Engels, S Heuer, A Houben, T Hoeschen, B Jasper, et al. Materials for DEMO and reactor applications—boundary conditions and new concepts. *Physica Scripta*, 2016(T167):014002, dec 2016.
- [3] Y. Ueda, K. Schmid, M. Balden, W. Coenen J., T. Loewenhoff, A. Ito, A. Hasegawa, c. Hardie, M. Porton, and M. Gilbert. Baseline high heat flux and plasma facing materials for fusion. *Nuclear Fusion*, 57(9):092006, jun 2017.
- [4] J.H. You, E. Visca, Ch. Bachmann, T. Barrett, F. Crescenzi, M. Fursdon, H. Greuner, D. Guilhem, P. Languille, M. Li, S. McIntosh, A.V. Mueller, J. Reiser, M. Richou, and M. Rieth. European DEMO divertor target: Operational requirements and material-design interface. *Nuclear Materials and Energy*, 9:171–176, dec 2016.
- [5] D. Stork, P. Agostini, J.L. Boutard, D. Buckthorpe, E. Diegele, S.L. Dudarev, C. English, G. Federici, M.R. Gilbert, S. Gonzalez, A. Ibarra, C. Linsmeier, A. Li Puma, G. Marbach, P.F. Morris, L.W. Packer, B.I Raj, M. Rieth, M.Q. Tran, D.J. Ward, and S.J. Zinkle. Developing structural, high-heat flux and plasma facing materials for a near-term DEMO fusion power plant: The eu assessment. *Journal of Nuclear Materials*, 455(1-3):277–291, 2014.
- [6] M. Rieth, S.L. Dudarev, S.M. Gonzalez De Vicente, J. Aktaa, T. Ahlgren, S. Antusch, D.E.J. Armstrong, M. Balden, N. Baluc, M.-F. Barthe, W.W. Basuki, M. Battabyal, C.S. Becquart, D. Blagoeva, H. Boldryeva, J. Brinkmann, M. Celino, L. Ciupinski, J.B. Correia, A. De Backer, C. Domain, E. Gaganidze, C. Garcia-Rosales, J. Gibson, M.R. Gilbert, S. Giusepponi, B. Gludovatz, H. Greuner, K. Heinola, T. Hoeschen, A. Hoffmann, N. Holstein, F. Koch, W. Krauss, H. Li, S. Lindig, J. Linke, C. Linsmeier, P. Lopez-Ruiz, H. Maier, J. Matejcek, T.P. Mishra, M. Muhammed, A. Munoz, M. Muzyk, K. Nordlund, D. Nguyen-Manh, J. Opschoor, N. Ordas, T. Palacios, G. Pintsuk, R. Pippan, J. Reiser, J. Riesch, S.G. Roberts, L. Romaner, M. Rosinski, M. Sanchez, W. Schulmeyer, H. Traxler, A. Urena, J.G. Van Der Laan, L. Veleva, S. Wahlberg, M. Walter, T. Weber, T. Weitkamp, S. Wurster, M.A. Yar, J.H. You, and A. Zivelonghi. A brief summary of the progress on the EFDA tungsten materials program. *Journal of Nuclear Materials*, 442(1-3 SUPPL.1):173–180, 2013.
- [7] Christian Bachmann, G. Aiello, R. Albanese, R. Ambrosino, F. Arbeiter, J. Aubert, L. Boccaccini, D. Carloni, G. Federici, U. Fischer, M. Kovari, A. Li Puma, A. Loving, I. Maione, M. Mattei, G. Mazzone, B. Meszaros, I. Palermo, P. Pereslavtsev, V. Riccardo, P. Sardain, N. Taylor, S. Villari, Z. Vizvary, A. Vaccaro, E. Visca, and R. Wenninger. Initial (DEMO) tokamak design configuration studies. *Fusion Engineering and Design*, 98-99:14231426, October 2015.
- [8] J.W. Coenen, J. Riesch, J-H You, M. Rieth, G. Pintsuk, H. Gietl, B. Jasper, F. Klein, A. Litnovsky, Y. Mao, et al. Advanced materials for a damage resilient divertor concept for DEMO: Powder-metallurgical tungsten-fibre reinforced tungsten. *Fusion Engineering and Design*, 124:964–968, dec 2017.
- [9] M.E.a Launey and R.O.a b Ritchie. On the fracture toughness of advanced materials. *Advanced Materials*, 21(20):2103–2110, 2009.

- [10] Gergely Czel and M.R. Wisnom. Demonstration of pseudo-ductility in high performance glass/epoxy composites by hybridisation with thin-ply carbon prepreg. *Composites Part A: Applied Science and Manufacturing*, 52(0):23–30, 2013.
- [11] Kazuya Shimoda, Joon-Soo Park, Tatsuya Hinoki, and Akira Kohyama. Influence of pyrolytic carbon interface thickness on microstructure and mechanical properties of SiC/sic composites by {NITE} process. *Composites Science and Technology*, 68(1):98–105, 2008.
- [12] F. Koch and H. Bolt. Self passivating W-based alloys as plasma facing material for nuclear fusion. *Physica Scripta T*, T128:100–105, mar 2007.
- [13] A. Litnovsky, T. Wegener, F. Klein, Ch. Linsmeier, M. Rasinski, A. Kreter, B. Unterberg, J.W. Coenen, H. Du, J. Mayer, C. Garcia-Rosales, A. Calvo, and N. Ordas. Smart tungsten alloys as a material for the first wall of a future fusion power plant. *Nuclear Fusion*, 57(6):066020, apr 2017.
- [14] A Litnovsky, T Wegener, F Klein, Ch Linsmeier, M Rasinski, A Kreter, X Tan, J Schmitz, J W Coenen, Y Mao, J Gonzalez-Julian, and M Bram. New oxidation-resistant tungsten alloys for use in the nuclear fusion reactors. *Physica Scripta*, T170:014012, sep 2017.
- [15] J. Riesch, M. Aumann, J.W. Coenen, H. Gietl, G. Holzner, T. Hoeschen, P. Huber, M. Li, Ch. Linsmeier, and R. Neu. Chemically deposited tungsten fibre-reinforced tungsten the way to a mock-up for divertor applications. *Nuclear Materials and Energy*, 9:75–83, may 2016.
- [16] H Gietl, J Riesch, JW Coenen, T Höschen, Ch Linsmeier, and R Neu. Tensile deformation behavior of tungsten fibre-reinforced tungsten composite specimens in as-fabricated state. *Fusion Engineering and Design*, 124:396–400, mar 2017.
- [17] A. von Mueller. "the effects of heat treatment on the mechanical properties of high-strength tungsten fibres for plasma-facing component composite material applications". To be published in *NME*, 2017. ICFRM - 18 International Conference on Fusion Reactor Materials.
- [18] Joseph R Stephens. Effects of interstitial impurities on the low-temperature tensile properties of tungsten. Technical report, NATIONAL AERONAUTICS AND SPACE ADMINISTRATION CLEVELAND OH LEWIS RESEARCH CENTER, 1964.
- [19] Y Mao, J Engels, A Houben, M Rasinski, J Steffens, A Terra, Ch Linsmeier, and JW Coenen. The influence of annealing on yttrium oxide thin film deposited by reactive magnetron sputtering: Process and microstructure. *Nuclear Materials and Energy*, 10:1–8, jan 2017.
- [20] J. Riesch, J.-Y. Buffiere, T. Hoeschen, M. di Michiel, M. Scheel, Ch. Linsmeier, and J.-H. You. In situ synchrotron tomography estimation of toughening effect by semi-ductile fibre reinforcement in a tungsten-fibre-reinforced tungsten composite system. *Acta Materialia*, 61(19):7060–7071, 2013.
- [21] J Riesch, T Hoeschen, Ch Linsmeier, S Wurster, and J-H You. Enhanced toughness and stable crack propagation in a novel tungsten fibre-reinforced tungsten composite produced by chemical vapour infiltration. *Physica Scripta*, 2014(T159):014031, 2014.
- [22] B. Jasper, S. Schoenen, J. Du, T. Hoeschen, F. Koch, Ch. Linsmeier, R. Neu, J. Riesch, A. Terra, and J.W. Coenen. Behavior of tungsten fiber-reinforced tungsten based on single fiber push-out study. *Nuclear Materials and Energy*, 9:416–421, may 2016.
- [23] B. Jasper et al. Powder metallurgical tungsten fiber-reinforced tungsten. *Material Science Forum, Trans Tech Publications*, 825-826:125–133, 2015.
- [24] J Riesch, Y Han, J Almanstötter, JW Coenen, T Höschen, B Jasper, P Zhao, Ch Linsmeier, and R Neu. Development of tungsten fibre-reinforced tungsten composites towards their use in DEMO—potassium doped tungsten wire. *Physica Scripta*, T167(T167):014006, jan 2016.
- [25] Y Mao, J W Coenen, J Riesch, S Sistla, J Almansttter, B Jasper, A Terra, T Hschen, H Gietl, M Bram, J Gonzalez-Julian, Ch Linsmeier, and C Broeckmann. Development and characterization of powder metallurgically produced discontinuous tungsten fiber reinforced tungsten composites. *Physica Scripta*, T170:014005, aug 2017.
- [26] H Bolt, V Barabash, G Federici, J Linke, A Loarte, J Roth, and K Sato. Plasma facing and high heat flux materials - needs for ITER and beyond. *Journal of Nuclear Materials*, 307311, Part 1(0):43–52, 2002.
- [27] Xunxiang Hu, Takaaki Koyanagi, Makoto Fukuda, NAP Kiran Kumar, Lance L Snead, Brian D Wirth, and Yutai Katoh. Irradiation hardening of pure tungsten exposed to neutron irradiation. *Journal of Nuclear Materials*, 2016.
- [28] M. Hubert et al. The absence of plasma in "spark plasma sintering". *J. Appl. Phys.*, 104(3):033305, 2008.
- [29] Cecile S Bonifacio, Troy B Holland, and Klaus van Benthem. Evidence of surface cleaning during electric field assisted sintering. *Scripta Materialia*, 69(11):769–772, 2013.
- [30] Cecile S Bonifacio, Troy B Holland, and Klaus van Benthem. Time-dependent dielectric breakdown of surface oxides during electric-field-assisted sintering. *Acta Materialia*, 63:140–149, 2014.
- [31] Joanna R Groza and Antonios Zavaliangos. Sintering activation by external electrical field. *Materials Science and Engineering: A*, 287(2):171–177, 2000.
- [32] P. Zhao, J. Riesch, T. Hoeschen, J. Almanstoeetter, M. Balden, J.W. Coenen, W. Himml, W. Pantleon, U. Toussaint, and R. Neu. Microstructure, mechanical behaviour and fracture of pure tungsten wire after different heat treatments. *International Journal of Refractory Metals and Hard Materials*, In Press, 2017.